

Synthesis, Characterization, and Magnetism of Dendrimer Encapsulated Co Nanoparticles

Marquita D. Bradshaw, Marc R. Knecht, and Richard M Crooks*

*Contribution from the Department of Chemistry, Texas A & M University, P.O. Box 30012,
College Station, Texas 77844-3012*

Preparation and characterization of magnetic Co dendrimer-encapsulated nanoparticles (DENs) have been studied. As these materials are easily oxidized, the synthesis was carried out under anaerobic conditions in organic solvents. Using a hydrophobically modified G6-PAMAM dendrimer template, DENs consisting of 55 and 147 Co atoms were prepared using a single-phase direct reduction technique. Characterization of the DENs by UV-vis spectroscopy and transmission electron microscopy (TEM) indicated the synthesis of particles. The materials are nearly monodisperse with average particle diameters > 0.9 nm with dispersities of 0.2 nm. Magnetic studies of both sized DENs indicate that they are superparamagnetic with hysteresis-free magnetism. These resultant effects are directly correlated to the particle size, which has been shown to significantly affect their resultant behavior.

Introduction

Dendrimer-encapsulated nanoparticles (DENs) are synthesized by a template approach in which metal ions are loaded into the interior of polyamidoamine (PAMAM) dendrimers and then chemically reduced. This effect yields nearly size-monodisperse particles having dimensions of less than 3 nm.² This method was initially demonstrated by preparation of Cu clusters, but the approach was further applicable to many other transition metals including Pt, Pd, Au, and Ag.^{3,7,12,13}

We have previously shown that DENs can be rendered soluble in a variety of solvents by controlling the chemistry of their periphery.⁴ The chemical composition of the peripheral groups on the dendrimer described here were modified to contain dodecyl groups which provided a means for solubilizing them in organic solvents. This hydrophobic characteristic allows for production of DENs of easily oxidizable metals, such as Co. Production of such

particles was previously unable to be performed under aqueous conditions. DENs composed of easily oxidizable metals are of particular interest because of their superparamagnetic properties. An advanced understanding of these DENs will pave the way for bimetallic DENs composed of alloyed mixtures of these metals as precursors and moreover, preparation of these DENs will expand the range of studies in catalysis, magnetism, and optics.

Experimental Section


Materials. Amine terminated, sixth-generation PAMAM dendrimers substituted on the periphery with dodecyl functional groups (G6-C₁₂) were purchased from Dendritech (Midland, MI) as a 10.0% wt solution in toluene. The manufacturer indicates that 50% of the 128 H atoms on the surface of the dendrimer are substituted by dodecyl groups. Prior to use, the toluene was

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 2005		2. REPORT TYPE N/A		3. DATES COVERED -	
4. TITLE AND SUBTITLE Synthesis, Characterization, and Magnetism of Dendrimer Encapsulated Co Nanoparticles				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Texas A & M University, College Station, Texas 77844-3012				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release, distribution unlimited					
13. SUPPLEMENTARY NOTES The original document contains color images.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UU	18. NUMBER OF PAGES 5	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

removed under vacuum at 25°C, and a 200 μ M stock solution of G6-C₁₂ was prepared in toluene. CoCl₂, THF, and NaEt₃BH were purchased from the Aldrich Chemical Company (Milwaukee, WI) and used as received.

Characterization. UV-Vis absorbance spectra were obtained using a Hewlett-Packard HP8453 spectrometer and quartz cuvettes having a pathlength of 1.00 cm. The spectrum of either toluene or THF was used as a reference depending on the solution being analyzed. Transmission electron microscopy (TEM) images were obtained using a JEOL-2010F TEM operating at 200kV and having a resolution of 0.14 nm. Samples were prepared by dropwise addition of the sample onto a holey-carbon-coated Cu grid (EM Sciences, Gibbstown, NJ).

Preparation of Co DENs. 50 μ L of the 200 μ M G6-C₁₂ stock solution was diluted in toluene or THF to a concentration of 2.00 μ M. The dendrimer/metal ion complexes (G6-C₁₂(Co²⁺)₅₅ and (G6-C₁₂(Co²⁺)₁₄₇) were prepared by introducing 55 or 147 mol equiv., respectively, of a freshly prepared 38.0 mL CoCl₂ solution in THF to the dendrimer solution. The final volume of these solutions was 5.00 mL. After stirring the solutions for 5 min., 100 μ L of a 1.0 M NaEt₃BH solution in toluene was added to finalize the synthesis of the Co DENs. 5 minutes elapsed after reduction before the DENs were analyzed.

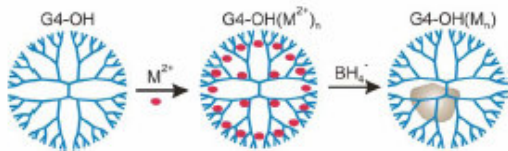

Results and Discussion

It has been previously shown that Au nanoparticles could be synthesized within hydrophobic dendrimers.¹³ To expand their use, we exploited this functionality to produce DENs of the easily oxidizable metal Co. By this production method, in organic solvents under anaerobic conditions, oxidants such as water and oxygen can be removed from the system preventing premature particle oxidation.

Co DENs were prepared in toluene and THF by an addition of CoCl₂ to a 2.0 μ M solution of G6-C₁₂ prepared under nitrogen. This solution yielded a pale blue color and no visual evidence of precipitation. After reduction, the solution turned a deep brown color with no further evidence of precipitation. Reduction occurred rapidly after the addition of the NaEt₃BH.

UV-vis spectra obtained after each step of synthesis of G6-C₁₂(Co₅₅) are provided in Figure 1. There is an apparent difference in the bands as well as wavelength shift of each spectra which indicates the breaking and formation of bonds as the solutions differ.

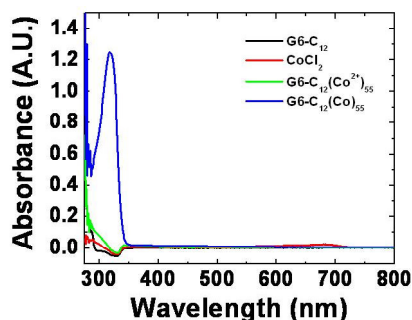


Figure 1. UV-Vis spectra of G6-C₁₂(Co₅₅) before and after reduction. Also shown are G6-C₁₂ alone and a 110 μ M spectra of CoCl₂.

Figure 2 shows the TEM images and particle-size distributions for G6-C₁₂(Co₅₅) and G6-C₁₂(Co₁₄₇). Analysis of over 100 particles yielded sizes of 0.9 ± 0.2 and 1.2 ± 0.2 nm for Co₅₅ and Co₁₄₇ DENs respectively. These diameters are comparable to the calculated diameters of G6-C₁₂(Co₅₅) and G6-C₁₂(Co₁₄₇), which are 0.9 and 1.3 nm respectively.²

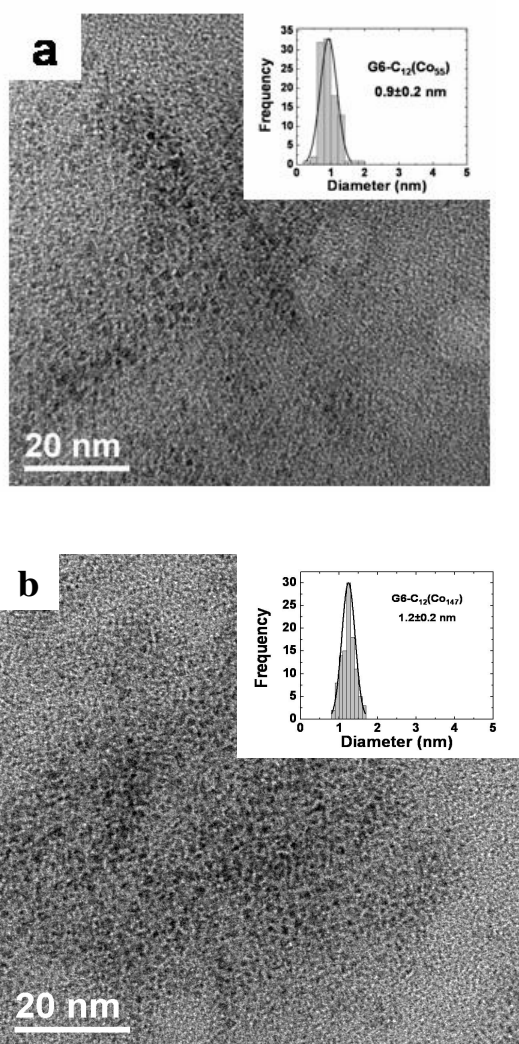


Figure 2. TEM images and size distribution for G6-C₁₂(Co₅₅) (a).and G6-C₁₂(Co₁₄₇) (b).

Conclusion. It is evident that dendrimer-encapsulated nanoparticles have been synthesized according to characterization.

Dendrimer-encapsulated Co nanoparticles are expected to yield superparamagnetic activity with hysteresis-free magnetism in agreement with previous studies performed on Ni DENs.¹⁵ We have shown that DENs composed of easily oxidizable metals such as Co can be synthesized within hydrophobic dendrimer templates. Characterization of these DENs paves the way for innovative applications in the fields of magnetism and catalysis. Studies concerning bimetallic Co nanoparticles are underway and will soon be reported. Together, these studies represent an advancement in understanding the effects of the nanoscale on magnetic materials. This effect is important due to the viability of magnetic storage devices as the recordable surface area decreases towards the superparamagnetic domain.

Acknowledgments. We acknowledge the sponsorship of this research by NASA Cooperative Agreement No. NCC-1-02038, NSF Award No. 0453578 and the Look College of Engineering USRG Program. We would also like to thank the Microscopy and Imaging Center at UT Austin for assistance with TEM images, the Crooks Group for insight on research in electrochemistry, and Dr. Daniel C. Davis and the TiiMS program for the opportunity to conduct research at Texas A & M University

References and Notes

- (1) Crooks, R. M.; Zhao, M.; Sun, L.; Chechik, V.; Yeung, L. K. Dendrimer-Encapsulated Metal Nanoparticles: Synthesis,

- Characterization, and Application to Catalysis. Acc. Cehm. Res. 2001, 34, 181-190.
- (2) Scott, R. W. J.; Wilson, O.M.; Crooks, R.M. Synthesis, Characterization, and Applications of Dendrimer-Encapsulated Nanoparticles. J. Phys. Chem. B 2005, 109, 692-704, and references therein.
- (3) Wilson, O. M.; Scott, R. W. J.; Garcia-Martinez, J.C.; Crooks, R. M. Synthesis, Characterization, and Structure-Selective Extraction of 1-3 nm Diameter AuAg Dendrimer-Encapsulated Bimetallic Nanoparticles. J. Am. Chem. Soc. 2005, 127, 1015-1024.
- (4) Nui, Y.; Crooks, R. M. Preparation of Dendrimer-Encapsulated Metal Nanoparticles Using Organic Solvents. Chem. Mater. 2003, 15, 3463-3467
- (5) Leslie-Pelecky, D.L.; Rieke, R.D. Magnetic Properties of Nanostructured Materials. Chem. Mater. 1996, 8, 1770-1783.
- (6) Mingqi, Z.; Sun, L.; Crooks, R.M. Preparation of Cu Nanoclusters within Dendrimer Templates. J. Am. Chem. Soc. 1998, 120, 4877-4878
- (7) Scott, R. W. J.; Datye, A. K.; Crooks, R.M. Bimetallic Palladium-Platinum Dendrimer-Encapsulated Catalysts. J. Am. Chem. Soc. 2003, 125, 3708-3709
- (8) Wostek-Wojciechowska, D.; Jeszka, J.K., Amiens, C.; Chaudret, B., Lecante, P. The solid-state synthesis of metal nanoparticles from organometallic precursors. J. Colloid Interface Sci. 2005, 287, 107-113
- (9) Hormes, J.; Modrow, H.; Bönnemann, H.; Kumar, C.S.S.R.; The Influence of Various Coatings on the Electronic, Magnetic, and Geometric Properties of Cobalt Nanoparticles (invited). J. App. Phys., 2005, 97, 10R102-1-10R102-6
- (10) Gosmini, C.; Périchon, J. New and simple one step cobalt catalyzed preparation of functionalized arylstannanes from the corresponding aryl bromides or iodides. Org. Bionol. Chem. 2005, 3, 216-217
- (11) Fillon, H.; Gosmini, C.; Périchon, J. A Convenient Method for the Preparation of Aromatic Ketones from Acyl Chlorides and Arylzinc Bromides Using A Cobalt Catalysis. Tetrahedron. 2003, 59, 8199-8202
- (12) J. C. Garcia-Martinez; R. Lezutekong; R. M. Crooks Dendrimer-Encapsulated Pd Nanoparticles as Aqueous, Room-Temperature Catalysts for the Stille Reaction J. Am. Chem. Soc. 2005 127 5097-5103
- (13) Garcia-Martinez, J. C. and Crooks, R. M. Extraction of Au Nanoparticles Having Narrow Size Distributions from within Dendrimer Templates J. Am. Chem. Soc. 2004 126 16170-16178
- (14) Y.-G. Kim; S.-K. Oh; R. M. Crooks Preparation and Characterization of 1-2nm Dendrimer-Encapsulated

Gold Nanoparticles having
Very Narrow Size-
Distributions *Chem. Mater.*
2004 *16* 167-172

- (15) Chai, Minghui; Holly, Aaron K.;
Norton, Michael L. Synthesis
and characterization of PPI-3
encapsulated metal nanoparticles.
Polymer Preprints (American
Chemical Society, Division of
Polymer Chemistry) **2003** *44*(2),
296-297.